

Synthesis and characterization of novel compounds and determining their antifungal properties against rainbow trout pathogen, *Saprolegnia* sp. *in vitro*

Shokouh Saljoghi Z.^{1*}; Farhadian O.¹; Ramezani N.²; Mehraban Sangatash M.³

Received: December 2017

Accepted: February 2018

Abstract

Saprolegnia growth on trout eggs is a problem frequently encountered in fish hatcheries worldwide. In the present study silver nanoparticles (Ag NPs) were effectively grafted on the zeolite and bentonite framework using the chemical reduction method. Zeolite and bentonite, silver nitrate (AgNO₃), and sodium borohydride (NaBH₄) were used as inorganic solid supports, a silver precursor, and a chemical reduction agent, respectively. Silver ions were introduced into the porous zeolite through an ion-exchange path, in the external and interlamellar space of bentonite at room temperature. AgNO₃ and NaBH₄ were used as a silver precursor and reducing agent, respectively. The Ag/zeolite and Ag/bentonite nano compounds were characterized by Field Emission Scanning Electron Microscopy (FESEM), Fourier Transform Infrared (FTIR), X-ray powder diffraction (XRD), Energy-dispersive X-Ray spectroscopy (EDX) analysis. The results showed that Ag NPs form a spherical shape with uniform homogeneity in the particle size. The antifungal activity of Ag NPs in zeolites and bentonite were investigated against *Saprolegnia* sp. with different loads of nano composites and exposure time. All Ag/zeolite NCs and Ag/bentonite NCs were found to have antifungal activities. These results revealed that Ag NPs could be used as effective growth inhibitors in different biological systems, for instance in aquatic animal hatchery facilities.

Keywords: Antifungal properties, *Saprolegnia*, Nano silver, Zeolite, Bentonite, *Saprolegnia* growth index

1-Department of Natural Resources, Isfahan University of Technology, Isfahan, Iran

2-Department of Chemistry, Faculty of Science, Ferdowsi University of Mashhad, Mashhad, Iran

3-Food Quality and Safety Research Group, Food Science and Technology Research Institute, ACECR, Mashhad, Iran

*Corresponding author's Email: zoheirsaljoghi@gmail.com

Introduction

Fish diseases outbreaks are among the most important problems and challenges of aquaculture development in the world. The main cause of economic losses in aquaculture is diseased fish, and oomycete (water mold) infections rank second to bacterial diseases (Meyer, 1991). Infections by oomycete including *Saprolegnia* and *Aphanomyces* species are responsible for infections in aquaculture (Humphrey, 1893). Oomycetes such as Saprolegniales, including the *Saprolegnia*, *Achlya*, and *Aphanomyces* species, have been found responsible for fish infections in aquaculture, fish farms, and hobby fish tanks (Willoughby and Pickering 1977; Baldauf *et al.*, 2000). The genus *Saprolegnia* is responsible for significant fungal infections involving both dead and live fish as well as eggs in the aquaculture industry (Pickering and Willoughby, 1982; Noga, 1993; Ke *et al.*, 2009; Shahbazian *et al.*, 2010). *Saprolegnia* infections are endemic to all freshwater fish around the world and are partly responsible for the decline of natural populations of salmonids and other freshwater finfish species (Van West, 2006).

The efficacy of several antifungal compounds against growth of *Saprolegnia* has been studied. Antifungal agents are essential for the maintenance of healthy stocks of fish and their eggs in intensive aquaculture operations. The efficacy of antifungal compounds in the presence of excretory products was noted by Willoughby and Roberts (1992), who found that

Saprolegnia parasitica zoospores in pure water were sensitive to a combination of penicillin and streptomycin. The search for alternative methods and compounds for the control of oomycete outbreaks has increased, and the effectiveness of many potential oomycetocides has been tested using *in vitro* screening methods.

Bailey and Jeffrey (1989) examined more than 200 compounds to determine their inhibitory activity against potentially pathogenic oomycetes, such as flagellate and *S. hypogyna*. Minimum inhibitory concentrations for each compound were also reported. The use of chemicals against fungal diseases in aquaculture is very common. Malachite green was successfully used for treating all infectious stages of saprolegnia in fish aquaculture facilities (Foster and Woodbury, 1936; Olah and Farkas, 1978; Bailey, 1984; Alderman, 1985; Willoughby and Roberts, 1992). However, since the turn of the century, the use of malachite green has been banned worldwide due to its carcinogenic properties. Several studies revealed the toxicological effect (Bills *et al.*, 1977; Meyer and Jorgenson, 1983) and potentially mutagenic properties (Clemmensen *et al.*, 1984; Fernandes *et al.*, 1991; Srivastava *et al.*, 2004) of malachite green. Formalin, aqueous solution containing formaldehyde, has been widely used to control oomycete infection in aquaculture (Cline and Post, 1972; Walser and Phelps, 1993). Similar to malachite green such concerns make it unlikely that formalin will be considered for widespread use in the

short term and, in fact, it is likely to be banned in the future (Abd El-Gawad *et al.*, 2015).

Hydrogen peroxide is also effective against a variety of organisms, namely bacteria, yeasts, viruses, fungal and oomycete spores, and is potentially an important oomycetocide for fish culture, with negligible environmental impacts (Schreier *et al.*, 1996). Copper containing compounds are usually effective as fungistatic agents when used at high concentrations (Somers, 1967; Richmond, 1977). Other chemical compounds like bronopol (Pyceze©) (Pottinger and Day, 1999; Branson, 2002), iodophores (Muzzarelli *et al.*, 2001), ozone (Forneris *et al.*, 2003) along with non-chemical treatment methods including ultraviolet irradiation (Rahkonen and Koski, 2002), probiotics (Hatai and Willoughb, 1988; Petersen *et al.*, 1994; Hussein and Hatai, 2001; Lategan and Gibson, 2003; Lategan *et al.*, 2004), immunization and vaccines (Fregeneda-Grandes and Olesen, 2007) are used.

Various inorganic silver containing antibacterial and antifungal materials have been developed and some products commercially available (Yamamoto *et al.*, 1996; Hansel *et al.*, 1998; Xu *et al.*, 2011). Various antibacterial heavy metals are known to have a wide and relatively safe antibacterial spectrum (Cho *et al.*, 2005; Oya, 1996). Silver, copper, zinc, and other antibacterial metals, when bound to inorganic carriers designed for slow release are far superior as inorganic disinfectants in terms of safety, duration of action and resistance

to heat when compared with conventional organic agents (Top and Ulkü, 2004). For this reason, the development of inorganic bactericides and disinfectants composed of silver bound to various inorganic carriers for application in domestic and industrial fields is receiving extensive attention (Iwata, 1996). Accordingly, due to the lack of information on the antimicrobial effects of nano silver zeolite and specially nano silver bentonite on fish pathogens, the present study has been designed to examine the *in vitro* inhibitory properties of nano silver inorganic materials against saprolegnia.

Materials and methods

Chemicals

Reagents are of analytical grades and used as received without further purification. AgNO₃ (Merck, Germany, 99.98%) was used as the silver precursor. Bentonite, natural clay, was obtained from Tabas, Iran, and used without any further purification. The natural zeolitic tuff (clinoptilolite), provided from Semnan, Iran, NaBH₄ (98.5%) and HNO₃ (90%) used as reducing and digestion agents were obtained from Merck (Germany). All aqueous solutions were prepared in double distilled water.

Synthesis of Ag zeolite and bentonite nanocomposites by using NaBH₄

To synthesis Ag/Bentonite NCs and Ag/Zeolite NCs the silver contents of the samples, 5.0 g Ag 100g⁻¹ zeolite and bentonite was used. Constant amounts of sodium zeolite and bentonite were suspended in 0.001 M AgNO₃ solution

and stirred for 1 week at room temperature to obtain the AgNO₃/Bentonite and Zeolite suspension and completed cation exchange. A freshly prepared NaBH₄ (4×10^{-2} M) solution was then added to the suspensions under continuous stirring to reach a constant AgNO₃/NaBH₄ molar ratio (1:4).

Afterwards, stirring continued for an extra hour. The suspensions of Ag/MMT and Ag/ZEO NCs obtained were then centrifuged at 15,000 rpm for 40 minutes, and the precipitates were washed several times using distilled water in order to remove the silver ion residue, and dried overnight at 100°C (Figs. 1 and 2).

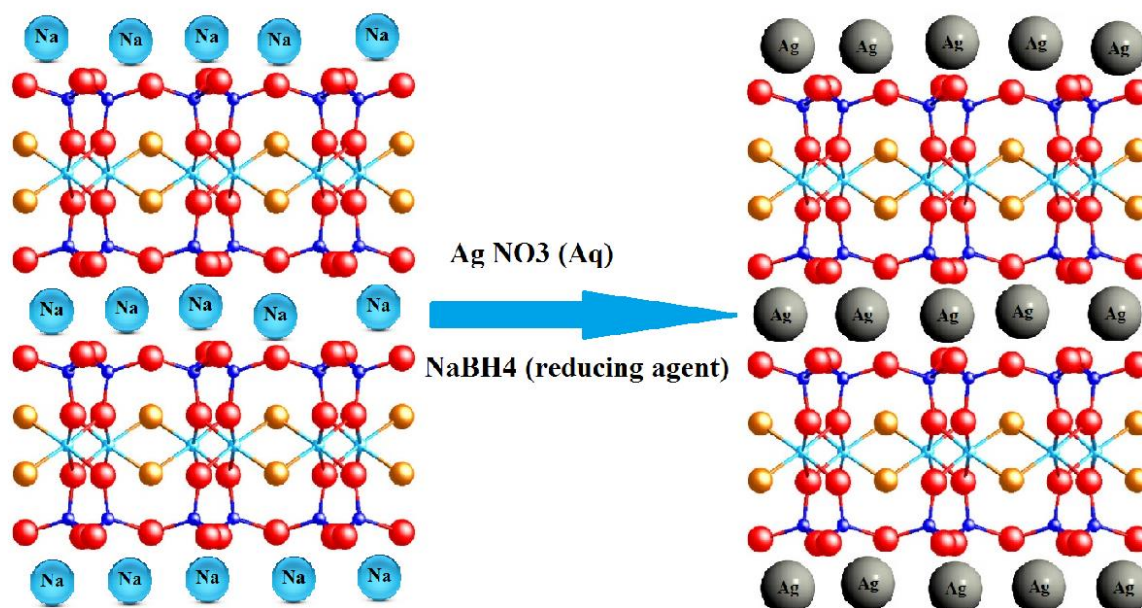


Figure 1: Schematic diagram of synthesis of Ag/bentonite NCs.

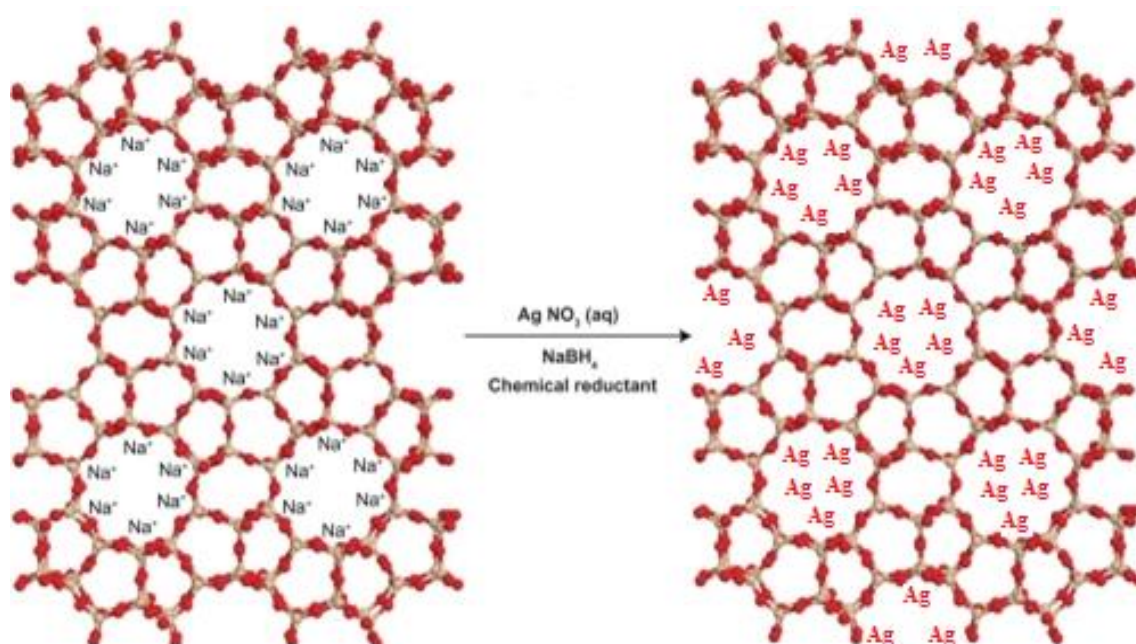


Figure 2: Schematic diagram of Synthesis of Ag/zeolite NCs.

Structural characterization methods and instruments

FTIR spectra of two types of Ag nanocomposites were recorded with KBr discs in the range of 4000–400 cm^{-1} on Nicolet AVATAR360 Fourier Transfer Infrared. FESEM images were taken by MIRA3 TESCAN (Czech).

Antifungal activity assays

A pure stock of fish *Saprolegnia* sp. previously isolated from rainbow trout eggs and characterized by the Department of Aquatic Animal Health, Veterinary Medicine Faculty, University of Tehran was used. The *Saprolegnia* sp. was cultured on a sabouraud dextrose agar (SDA) and stored at 4 °C until use. The antifungal activity of the Ag/zeolite and Ag/bentonite NCs were evaluated by determining the minimum inhibitory concentrations (MICs) using the agar dilution method (Bailey, 1983). The agar dilution method has been recommended as a standard *in vitro* antifungal susceptibility tests by the National Committee for Clinical Laboratory Standards (Dong, 2003). In brief, agar plugs containing fungal hyphae of *saprolegnia* (5 mm in diameter) removed from the edge of the pure stock were placed in the middle of depression spots on plates containing various concentrations of nanocomposites and incubated at 22 °C. The maximal growth of *saprolegnia* (colony diameter) was determined after 24, 48, 72, 96 and 120 h, respectively. To determine the inhibitory concentration range, ten test concentrations of two studied

nanocomposites 6.66, 13.33, 20, 26.66, 33.33, 40, 46.66, 53.33, 60 and 66.66 mg L^{-1} plus a negative control without nanocomposites were prepared on plates in triplicate. The growth of *saprolegnia* in the presence of the nanocomposites was compared to that of the control. To evaluate *saprolegnia* growth, the area over which the *saprolegnia* hyphae grew in the petri dishes was determined and compared to that of negative control (equation 1). The present study was conducted as a factorial experiment in a completely randomized design. Ten treatments and one control group, consisting of three replications for each group were used. Results were obtained by taking the mean of the three replicates in each group. The data obtained were analyzed by using SPSS software and Microsoft EXCEL. Comparison of mean results was performed using Duncan's multiple range test (DMRT).

Growth of *saprolegnia*
in the presence of
nanocomposites

$$\text{Saprolegnia growth index (\%)} = 100 \times \frac{\text{Growth of saprolegnia on the control plates}}{\text{Growth of saprolegnia in the presence of nanocomposites}}$$

Growth of
saprolegnia on the
control plates

Results

FTIR analysis of zeolite and Ag/zeolite NCs

Fig. 3 showed FT-IR spectra of the silicate host structure of zeolite and Ag/zeolite NCs. The FT-IR spectrum of zeolite showed vibration bands at 3450 cm^{-1} for O–H stretching due to the H_2O interporous structure of O–H stretching (H bonding), and at 1629 cm^{-1} for H–

O–H bending. The positions of the vibrational bands at 797–468 cm^{-1} corresponding to Si–O and other interstructure bands remained unchanged; a strong band at 1063 cm^{-1} was associated with the stretching vibration of Si–O, which usually suggests a three-dimensional silica phase. The band at 797 cm^{-1} was assigned to Al–O, and the position bands at 468 cm^{-1} were allocated to the Si–O–Si bending vibration. The FT-IR

spectra indicated the rigidity of silicate structure and nonband chemical interaction between the zeolite structure and Ag NPs in Ag/zeolite NCs. The interactions between the zeolite and Ag NPs were associated with the peak at 3448 cm^{-1} . A broad peak was due to the presence of van der Waals interactions between the hydroxyl groups in the zeolite structure related to H_2O and the partial positive charge on the Ag NPs surface.

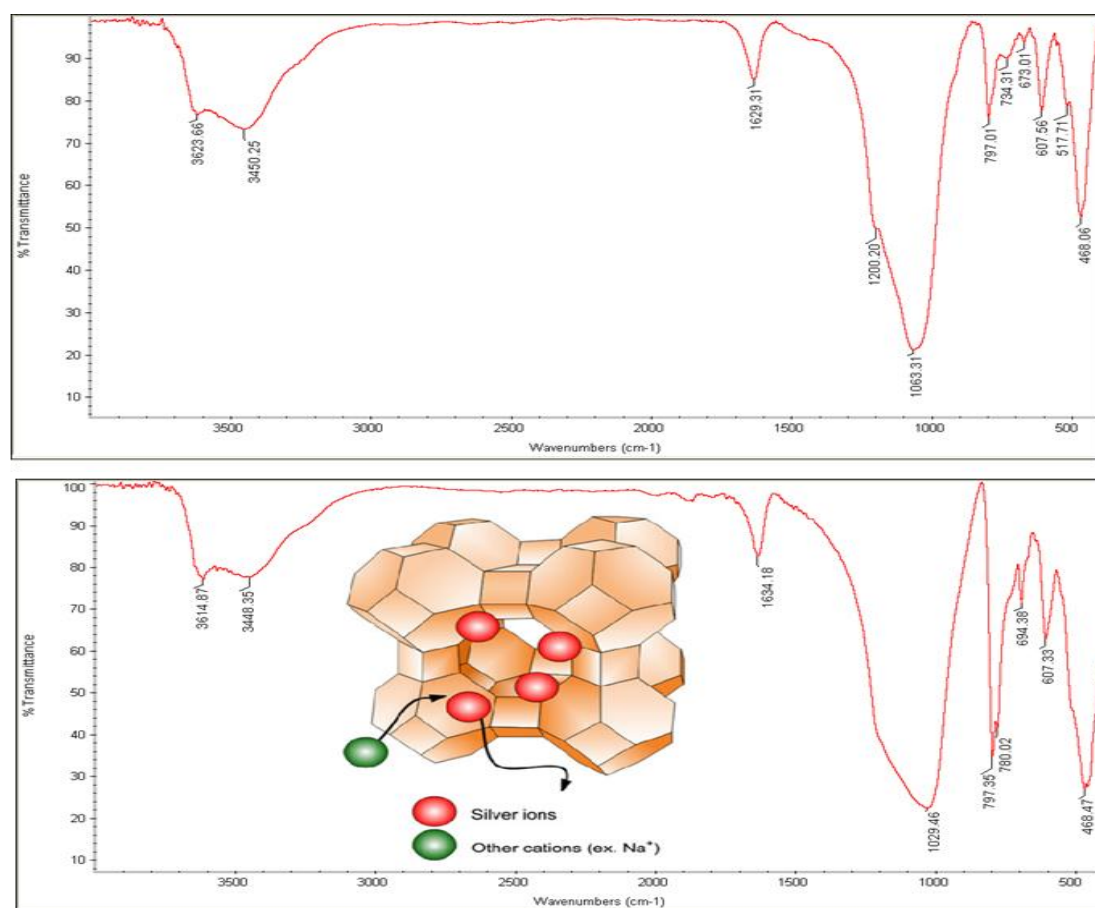


Figure 3: Fourier transform infrared spectra of zeolite and silver/zeolite nanocomposites.

FTIR analysis of zeolite and Ag/zeolite NCs

The FT-IR spectrum of raw bentonite (Fig. 4) showed the vibration bands at 3630 cm^{-1} for O–H stretching, 3444 cm^{-1} due to the inter-layered O–H

stretching (H bonding), at 1646 cm^{-1} for H–O–H bending, 1082, 1039, and 918 cm^{-1} for Si–O stretching, 624 cm^{-1} for Al–OH, 918 cm^{-1} due to (Al, Mg)–OH vibration modes, and 522 and 469 cm^{-1} for Si–O bending (Alemdar *et al.*,

2005). As shown in Fig. 2, there were not many changes in the spectra of Ag/BEN NCs compared with raw bentonite. The FT-IR spectra demonstrated the inflexibility of silicate

layers and non-bond chemical interface between the silicate layers and Ag NPs in Ag/ BEN NCs (Shameli *et al.*, 2010).

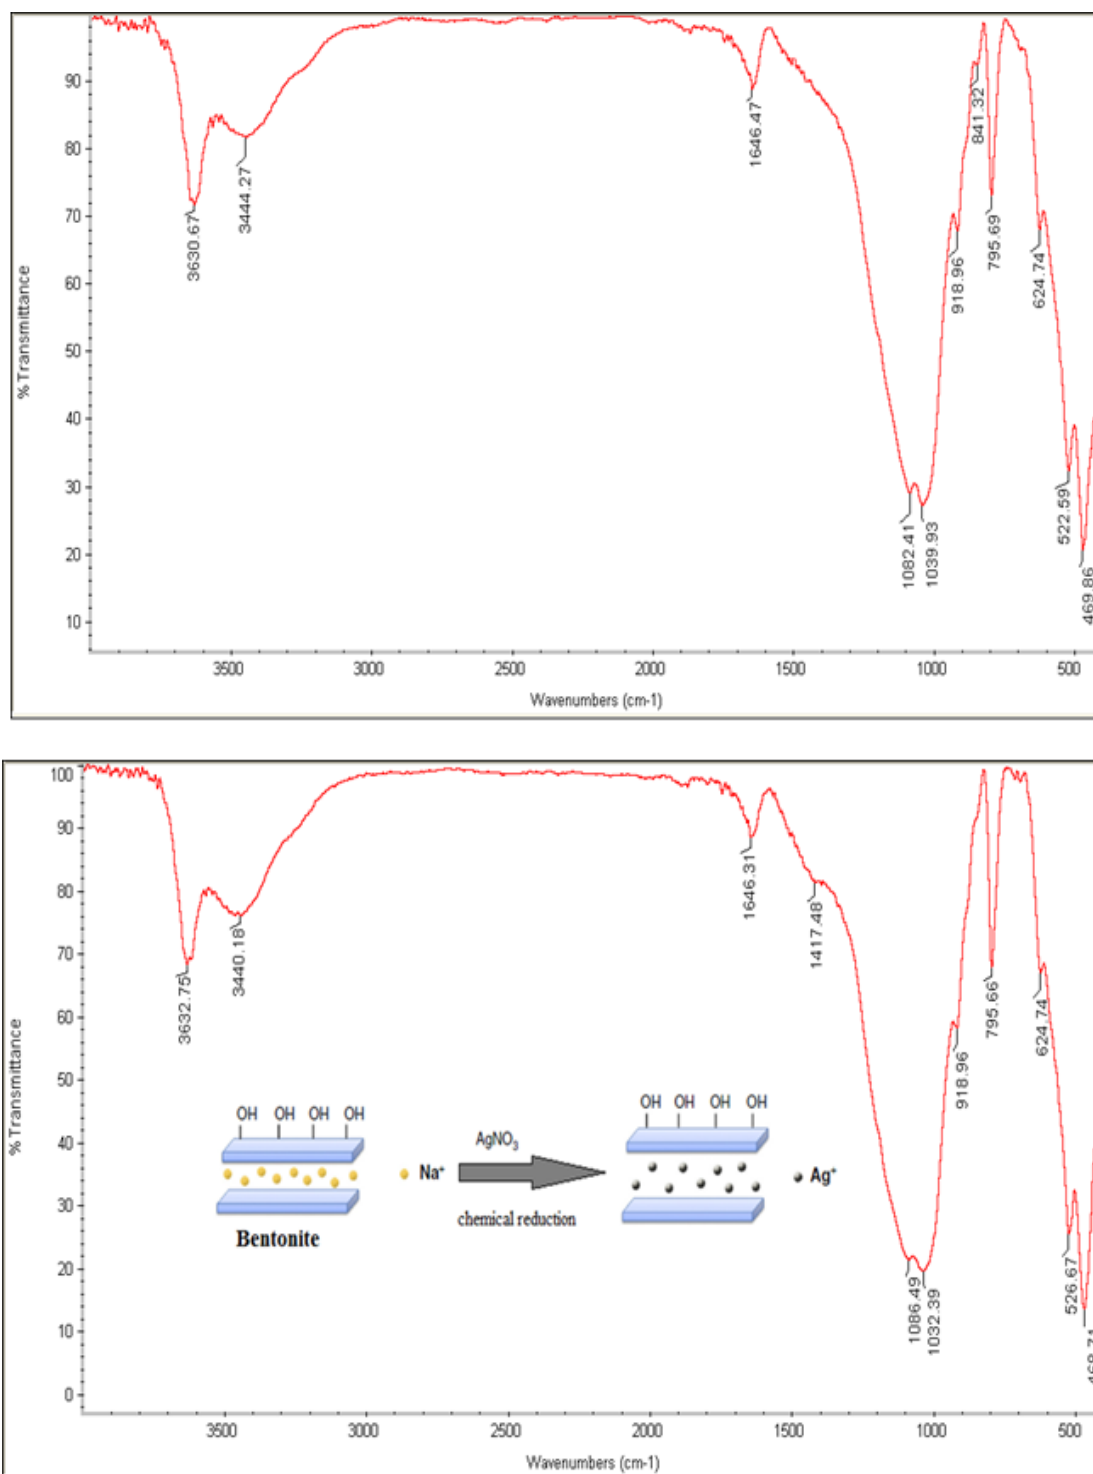


Figure 4: Fourier transform infrared spectra of bentonite and silver/bentonite nanocomposites.

XRD analysis of zeolite and nano Ag zeolite

To determine the crystalline phase of the nanosilver-coated zeolite, X-ray diffraction (XRD) was performed using an Explorer (Italy, GNR company), (Tube: Cu ka, Voltage: 40 kV, Current: 30 mA, detector type: Dectris (fast strip)). An X-ray diffract gram of the

AgNP-coated and uncoated natural zeolite was shown in Fig. 5. The XRD results indicated that clinoptilolite was the main phase present in the zeolite samples in this study. As seen in figure. 6, there was distinct difference in the XRD patterns of the AgNP-coated and uncoated zeolite samples.

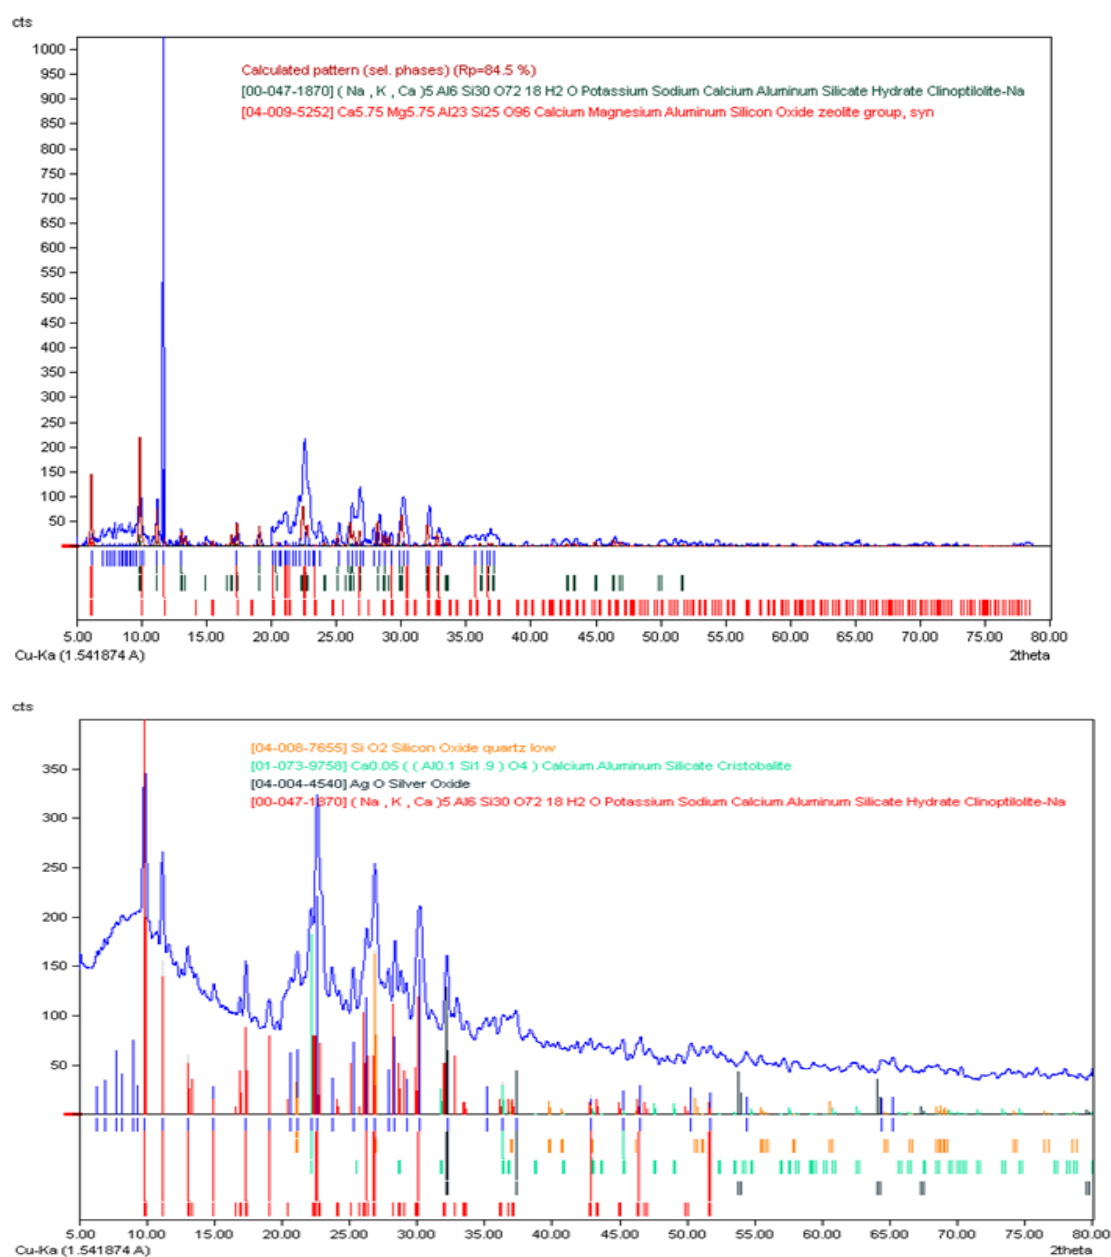


Figure 5: XRD analysis of raw zeolite (above) and silver nanoparticle-coated (below) zeolite.

XRD analysis of bentonite and nano Ag bentonite

The results of the characterization of bentonite by X Ray Diffraction showed that bentonite generally composed of four types of mineral; Sodium aluminum oxid zeolite, Cristobalite Quartz and Beidellite. The major clay

phase present was Beidellite. After nanoparticles of Ag were deposited on the clay, new peaks were observed corresponding to the formation Ag in the composite. XRD analysis for nanoAg bentonite showed that nano Ag particles were incorporated in bentonite structure (Fig. 6).



Figure 6: XRD analysis of raw bentonite (above) and silver nanoparticle-coated (below) bentonite.

Morphology of zeolite and Ag/zeolite NCs by FESEM

Fig. 7 presented the FE SEM images of the zeolite and Ag/zeolite NCs. The morphology of zeolite demonstrated a surface with a cubic shape, a typical structure for zeolite (Fig. 7 A). The

exterior morphology for Ag/zeolite NCs (7 B), also shows cubic forms without significant morphological differences. Furthermore, the external surfaces of Ag/zeolite NCs gradually become shinier due to the presence and increase of Ag NPs contents (Fig. 7 B).

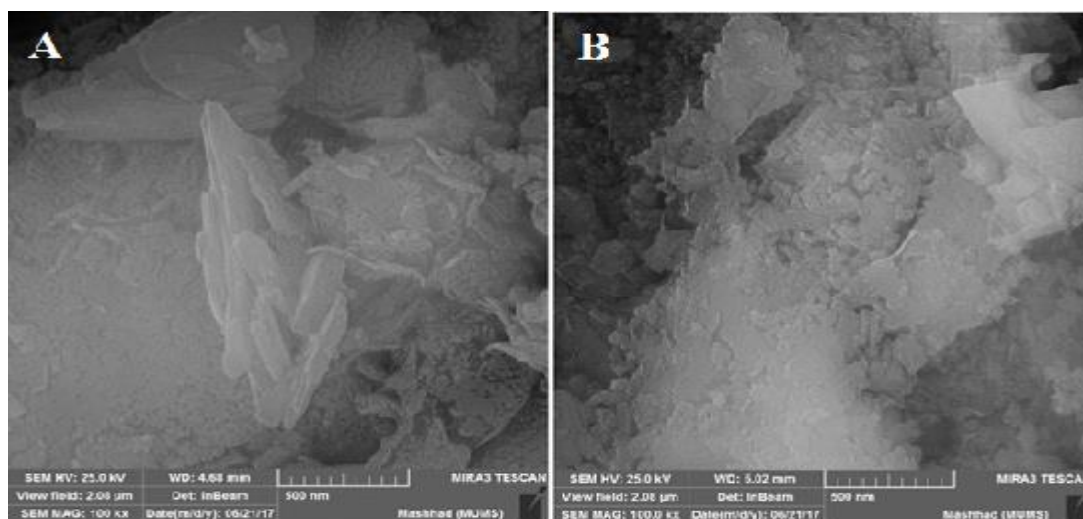


Figure 7: SEM micrographs of zeolite and silver/zeolite nanocomposites.

Morphology of bentonite and Ag/bentonite NCs by FESEM

SEM images of the raw bentonite and Ag/bentonite NCs are presented in Fig. 8. The surface morphology of bentonite demonstrated a layered surface with some large flakes, a typical structure of

bentonite (Fig. 8 A). The exterior morphology for Ag/bentonite NCs, showed layered surfaces with large flakes. However, significant morphological differences were observed (Fig. 8 B).

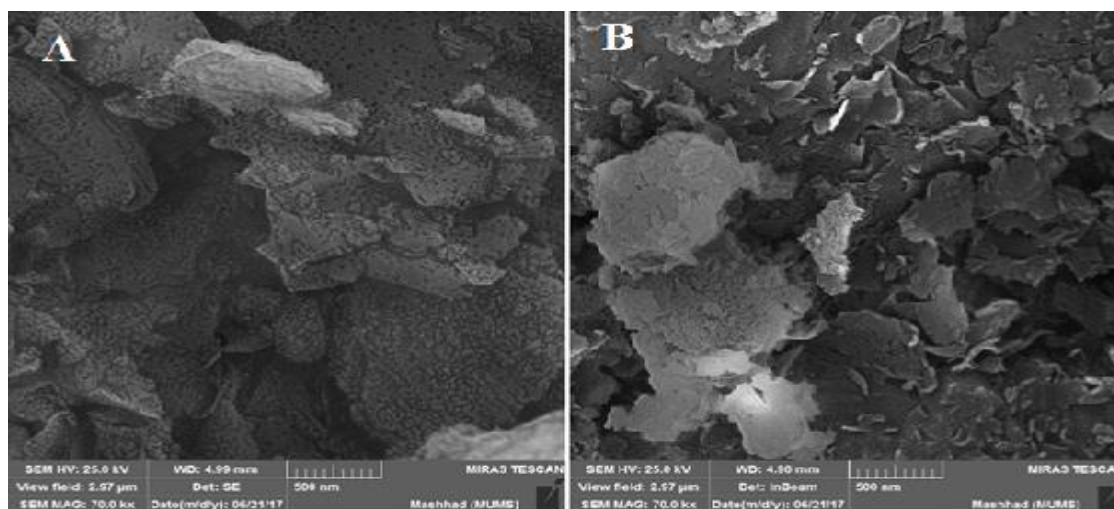


Figure 8: SEM micrographs of bentonite and silver/bentonite nanocomposites.

EDX analysis of raw and nano Ag containing zeolite and bentonite

The successful immobilization of Ag NPs was also confirmed by EDX analysis (Figs. 9 and 10), which showed the presence of Ag along with oxygen, aluminum and silica elements.

Concerning the results of XRD and SEM of the Ag/zeolite and Ag/bentonite nanocomposite, Ag NPs were fabricated and immobilized on the zeolite surface and bentonite framework.

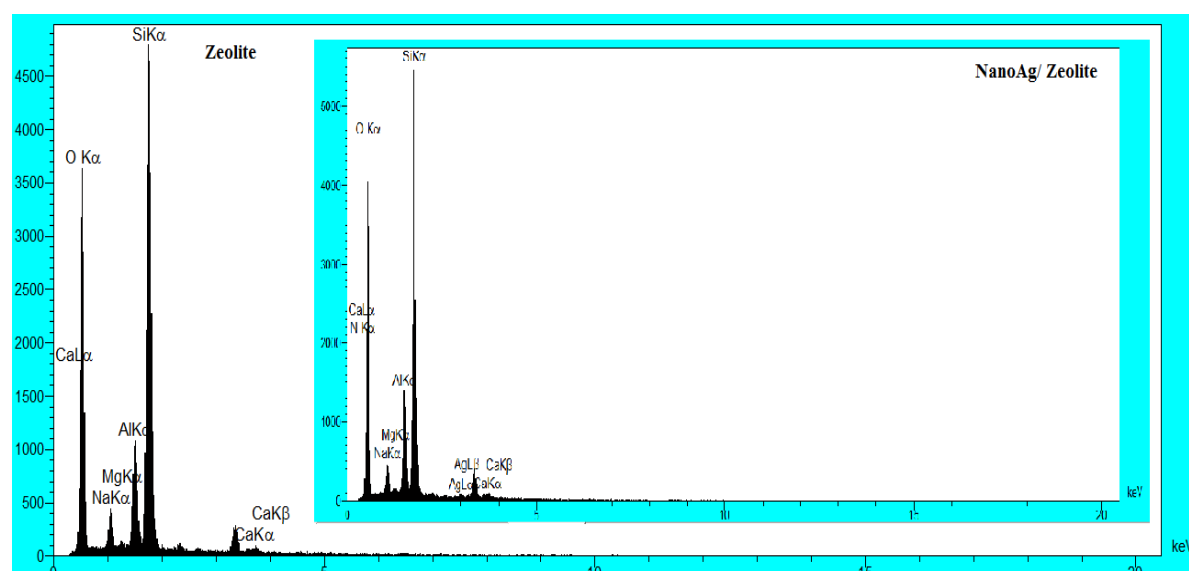


Figure 9: EDX analysis of natural and nano Ag zeolite.

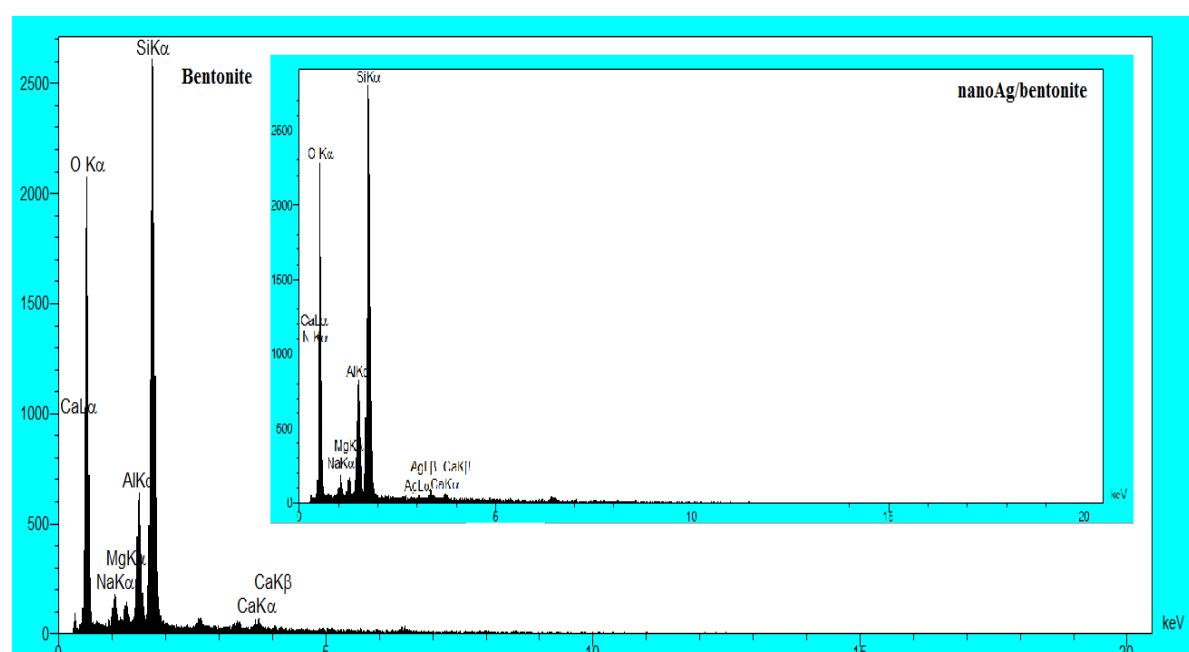


Figure 10: EDX analysis of natural and nano Ag zeolite.

Antifungal activity

The two Ag/zeolite and bentonite composites exhibited dose-dependent

activity against *Saprolegnia sp.* The results showed that at 6.66 and 13.33 mg/L of Ag/Zeolite NCS (Figs. 11 and

12) and at 6.66, 13.33, 20, 26.66, 33.33, 40, 46.66 mg L⁻¹ of Ag/Bentonite there were not any observable inhibitory effects compared to the negative control (without nano composites) (Figs. 13 and 14). The colonies grew well on the

control plates, where after 24 h the whole surface of the media was covered by *Saprolegnia sp.* hyphae. Our results showed that growth inhibition of *Saprolegnia sp.* was significant for Ag/Zelite NCS.

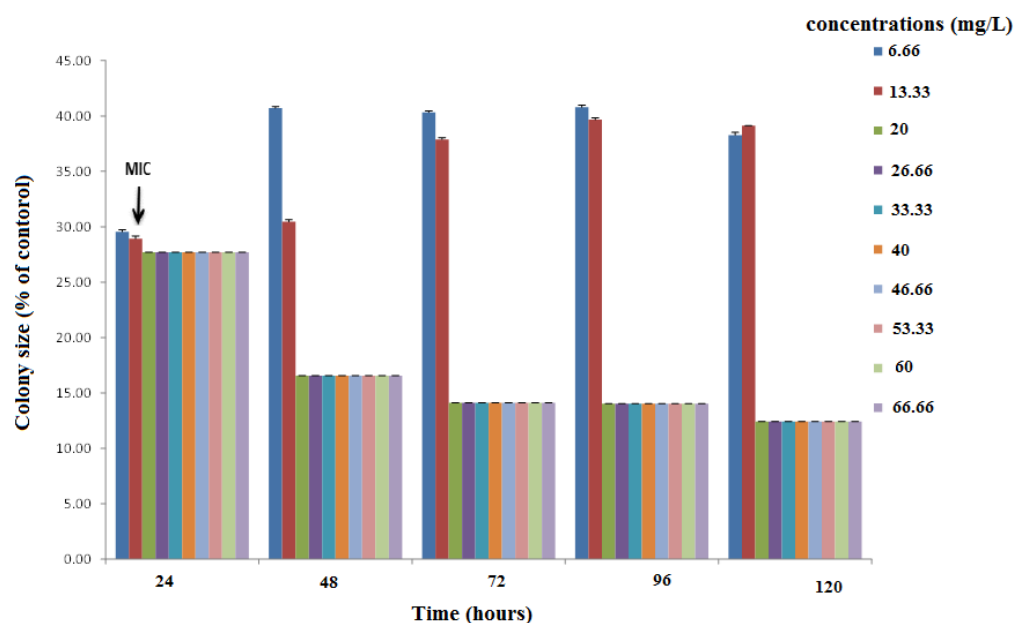


Figure11: Growth of *Saprolegnia* in different concentrations of Ag/zeolite NCs.

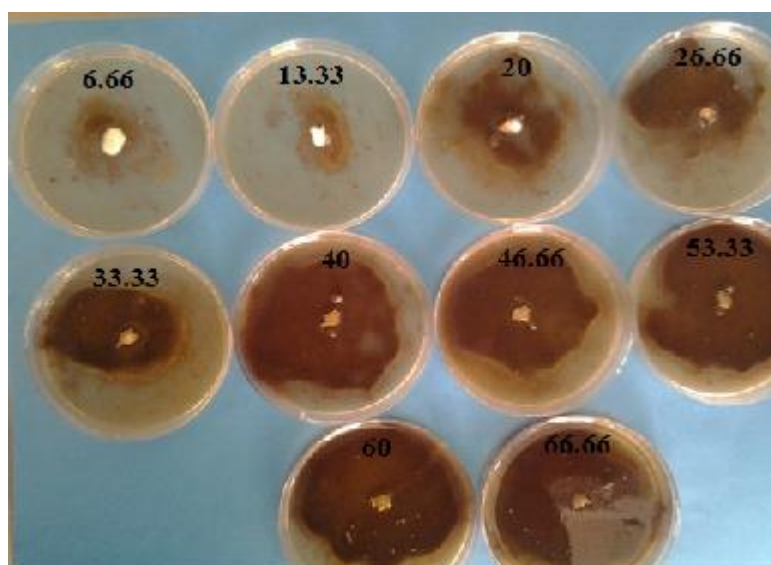


Figure 12: Growth of *Saprolegnia* on agar plates containing different concentrations of Ag/zeolite NCs.

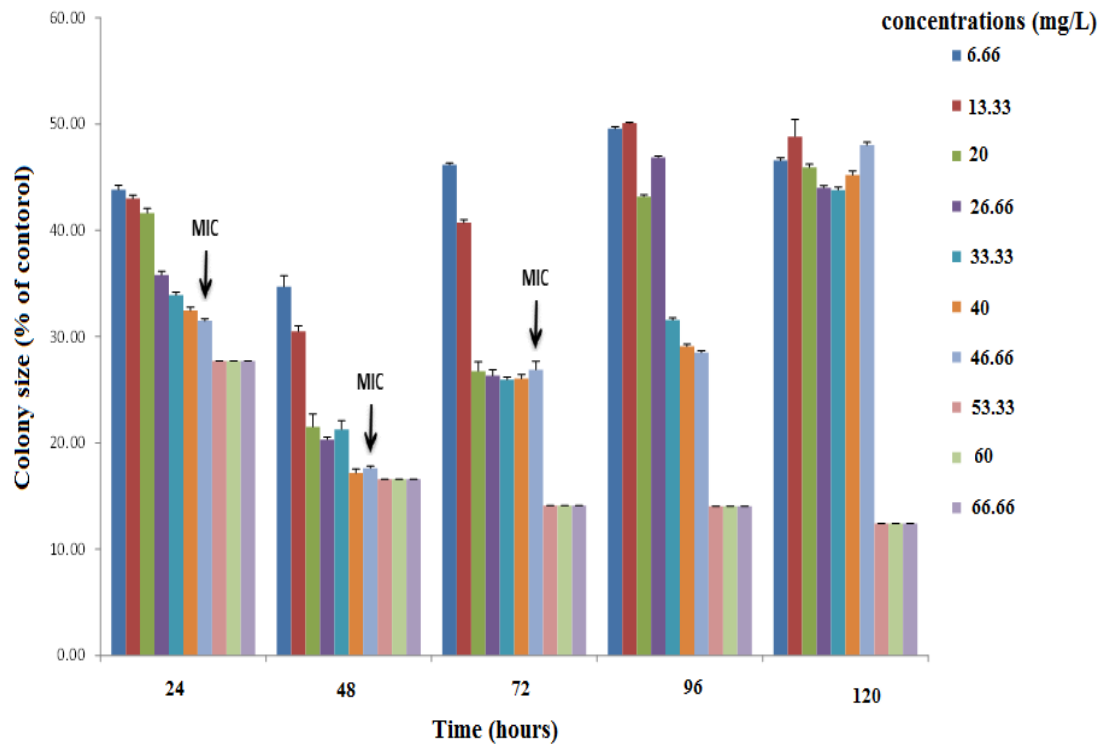


Figure 13: Growth of *Saprolegnia* in different concentrations of Ag/bentonite NCs.

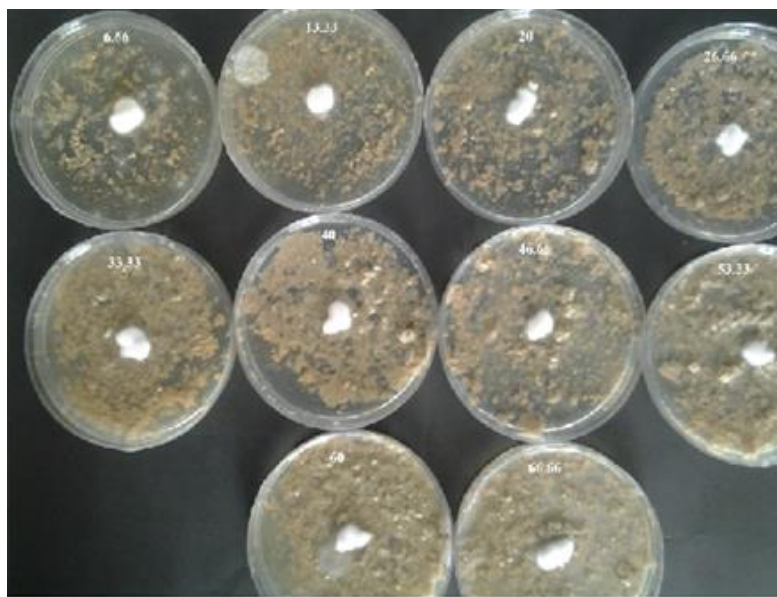


Figure 14: Growth of *Saprolegnia* on agar plates containing different concentrations of Ag/bentonite NCs.

Discussion

Silver nanoparticles (AgNPs) are known to have bactericidal and fungicidal effects. Since, there is little information available on the interaction of colloidal nanosilver with fish pathogens; the current study

investigated the effects of AgNPs on the growth of the *Saprolegnia* sp. *in vitro*. The antifungal activity of AgNPs was then evaluated by determining the minimum inhibitory concentrations (MICs) using two-fold serial dilutions of colloidal nanosilver in sabouraud

dextrose agar at 22 °C. The growth of *Saprolegnia* sp. on the AgNPs agar treatments was compared to that of nanosilver-free agar as controls. In the present study, AgNPs were found to inhibit the growth of the water mould *saprolegnia in vitro*, making AgNPs a good candidate for their indirect use in the aquaculture industry. It seems that AgNPs could be a proper replacement for teratogenic and toxic agents, such as malachite green. In addition, the indirect use of AgNPs could be a useful method for providing new antifungal activity in aquaculture systems.

Metallic silver in the form of silver nanoparticles has made a remarkable comeback as a potential antimicrobial agent. The use of silver nanoparticles is also important, as several pathogenic bacteria have developed resistance against various antibiotics. Silver ions have been known to have powerful antibacterial and antifungal activities (Sadjadi *et al.*, 2009). The mechanisms of antimicrobial activity of AgNPs have been extensively reported by several authors (Morones *et al.*, 2005; Kim *et al.*, 2007; Sanpui *et al.*, 2008; Rai *et al.*, 2009). AgNPs via changing and damaging the membrane structure of the microorganism (Kim *et al.*, 2007), increase the membrane permeability and also interrupt the efflux/influx of materials which subsequently results in microbial cell death. However their interaction with phosphorus and sulfur-containing compounds, such as DNA and proteins, inactivation of certain enzymes, attacking the respiratory chain, generating hydrogen peroxide and free radicals and the release of the

silver ions from the nanoparticles have been also reported (Feng *et al.*, 2000; Yoshihiro, 2002; Yamanaka *et al.*, 2005; Song *et al.*, 2006). Contrary to antibiotics resistance arising from irresponsible antibiotic application, silver has been demonstrated to be a consistently effective antimicrobial agent (Marambio-Jones and Hoek, 2010). Several authors have shown the inhibitory effect of silver on bacteria, viruses, and fungi (Prabhu and Poullose 2012; Johari *et al.*, 2013; Johari *et al.*, 2014). Heavy metals could react with proteins such as different enzymes via their -SH groups and leave them inactivated. Some researchers investigated the inhibition mechanism of silver ions on microorganisms (Prabhu and Poullose, 2012). Silver ions affect DNA molecules, causing the loss of replication abilities of DNA, and interact with thiol groups in protein thereby inactivating bacterial proteins. Many studies have been carried out on the antibacterial and antifungal properties of various natural and inorganic substances such as clinoptilolite, bentonite, montmorillonite and etc. (Top and Ulkü, 2004; Zhou *et al.*, 2004; Xu *et al.*, 2011).

The Ag NPs were successfully prepared from the AgNO₃/ bentonite and AgNO₃/ Zeolite suspension of the AgNO₃ solution by using sodium borohydride (NaBH₄) at room temperature. The surface of zeolite and bentonite fostered the nucleation of Ag NPs during the chemical reduction process. In the present study, the tested nanocomposites were found to inhibit

the growth of the *Saprolegnia in vitro*, making nanosilver zeolite and bentonite a potential candidate for indirect use in aquaculture. Indirect methods can be applicable in aquaculture systems such as fish ponds, hatcheries, and aquarium industries. In conclusion, further investigation of the antibacterial, antiviral, and antifungal activities of nano Ag zeolite and nano Ag bentonite against other fish pathogens is needed in the future.

In conclusion, further investigation of the antimicrobial activities of AgNPs against other fish pathogens is needed.

Acknowledgment

This research was financially supported by Isfahan University of Technology.

References

- Abd El-Gawad, Eman A., Shen, Zhi-Gang. and Wang, Han-Ping., 2015.** Efficacy of formalin, iodine and sodium chloride in improvement of egg hatching rate and fry survival prior to the onset of exogenous feeding in yellow perch Authors. *Aquaculture Research*, 47, 2461–2469.
- Alderman, D.J., 1985.** Malachite green: A review. *Journal of Fish Diseases*, 8, 289–298.
- Alemdar, A., Gungor, N. and Ece O.I., 2005.** The rheological properties and characterization of bentonite dispersions in the presence of non-ionic polymer PEG. *Journal of Material Sciences*, 40, 171–177.
- Bailey, T.A., Jeffrey, M., 1989.** Evaluation of 215 candidate fungicides for use in fish culture. US Fish and Wildlife Service, La Crosse. 9 P.
- Bailey, T.A., 1983.** Method for *in vitro* screening of aquatic fungicides. *Journal of Fish Disease*, 6, 91–100.
- Bailey, T.A., 1984.** Effects of twenty-five compounds on four species of aquatic fungi (*Saprolegniales*) pathogenic to fish. *Aquaculture*, 38, 97–104.
- Baldauf, S.L., Roger, A.J., Wenk-Siefert, I. and Doolittle, W.F., 2000.** A kingdom level phylogeny of eukaryotes based on combined protein data. *Science*, 290, 972–977.
- Bills, T.D., Marking, L.L. and Chandler, J.H., 1977.** Malachite green: Its toxicity to aquatic organisms, persistence and removal with activated carbon. *Investigation in Fish Control, Fish and Wildlife Leaflet*, 75, 6.
- Branson, E., 2002.** Efficacy of bronopol against infection of rainbow trout (*Oncorhynchus mykiss*) with the fungus *Saprolegnia* species. *Veterinary Record*, 151, 539–541.
- Cho, K.H., Park, J.E., Osaka, T. and Park, S.G., 2005.** The study of antimicrobial activity and preservative effects of nanosilver ingredient. *Electrochem Acta*, 51, 956–960.
- Clemmensen, S., Jensen, J.C., Jensen, N.J., Meyer, O., Olsen, P. and Würtzen, G., 1984.** Toxicological studies on malachite green: A triphenylmethane dye. *Archives of Toxicology*, 56, 43–45.
- Cline, T.F. and Post, G., 1972.** Therapy for trout eggs infected with

- Saprolegnia. *The Progressive Fish-Culturist*, 34, 148–151.
- Dong, X.X., 2003.** Methods for testing antibacterial activity of antibacterial materials. In: Ji JH, Shi WM, editors. *Antibacterial materials*. Beijing, China: Chemical Industry. 293 P.
- Fernandes, C., Lalitha, V.S. and Rao, K.V.K., 1991.** Enhancing effect of malachite green on the development of hepatic pre-neoplastic lesions induced by N-nitrosodiethylamine in rats. *Carcinogenesis*, 12, 839–845.
- Foster, F.J. and Woodbury, L., 1936.** The use of malachite green as a fish fungicide and antiseptic. *The Progressive Fish-Culturist*, 3, 7–9.
- Forneris, G., Bellardi, S., Palmegiano, G.B., Saroglia, M., Sicuro, B., Gasco, L. and Zoccarato, I., 2003.** Use of ozone in trout hatchery to reduce saprolegniasis incidence. *Aquaculture*, 221, 157–166.
- Fregeneda-Grandes, J.M. and Olesen, N.J., 2007.** Detection of rainbow trout antibodies against viral haemorrhagic septicaemia virus (VHSV) by neutralisation test is highly dependent on the virus isolate used. *Diseases of Aquatic Organisms*, 74, 151–158.
- Feng, Q.L., Wu J., Chen G.Q., Cui F.Z., Kim T.N. and Kim J.O., 2000.** A mechanistic study of the antibacterial effect of silver ions on *E. coli* and *Staphylococcus aureus*. *Journal of Biomedical Materials Research*, 52, 662–668.
- Hansel, C., Leyhausen, G., Mai, U.E. and Geurtsen, M., 1998.** W. Effects of various resin composite (co) monomers and extracts on two caries-associated microorganisms *in vitro*. *Journal of Dental Research*, 77, 60–67.
- Hatai, K. and Willoughby, L.G., 1988.** *Saprolegnia parasitica* from the rainbow trout inhibited by the bacterium, *Pseudomonas ferax*. *Transactions of the British Mycological Society*, 83, 257–263.
- Humphrey, J.E., 1893.** The Saprolegniaceae of the United States, with notes on other species. *Transactions of the American Philosophy Society*, 17, 63–148.
- Hussein, M.M.A. and Hatai, K., 2001.** *In vitro* inhibition of Saprolegnia by bacteria isolated from lesions of salmonids with saprolegniasis. *Fish Pathology*, 36, 73–78.
- Iwata, Y., 1996.** The latest trend of inorganic antibacterial agents. *Zeolite News Letters*, 13, 8–15.
- Johari, S.A., Kalbasi, M.R., Soltani, M. and Yu, I.J., 2013.** Toxicity comparison of colloidal silver nanoparticles in various life stages of rainbow trout (*Oncorhynchus mykiss*). *Iranian journal of fisheries sciences*, 12, 76–95.
- Johari, S.A., Kalbasi, M.R. and Yu, J., 2014.** Inhibitory effects of silver zeolite on *in vitro* growth of fish egg pathogen, *Saprolegnia* sp. *Journal of Coastal Life Medicine*, 2, 357–361.
- Ke, X.L., Wang, J.G., Gu, Z.M., Li, M. and Gong, X.N., 2009.** Morphological and molecular phylogenetic analysis of two *Saprolegnia* sp. (Oomycetes) isolated from silver crucian carp and

- zebra fish. *Mycological Research*, 113, 637–644.
- Kim, J.S., Kuk, E., Yu, K.N., Kim, J.H., Park, S.J., Lee, H.J., Kim, S.H., Park, Y.K., Park, Y.H., Hwang, C.Y., Kim, Y.K., Lee, Y.S., Jeong, D.H. and Cho, M.H., 2007.** Antimicrobial effects of silver nanoparticles. *Nanomedicine: Nanotechnology, Biology and Medicine*, 3, 95–10.
- Lategan M.J. and Gibson, L.F., 2003.** Antagonistic activity of *Aeromonas* media strain A1999 against *Saprolegnia* sp., an opportunistic pathogen of the eel, *Anguilla australis* Richardson. *Journal of Fish Diseases*, 26, 147–153.
- Lategan, M.J., Torpy, F.R. and Gibson, L.F., 2004.** Biocontrol of saprolegniosis in the eel, *Anguilla australis* Richardson, *Aeromonas* media strain A199. *Aquaculture*, 240, 19–27.
- Marambio-Jones, C. and Hoek, E.M.V., 2010.** A review of the antibacterial effects of silver nanomaterials and potential implications for human health and the environment. *Journal of Nanoparticle Research*, 12, 1531–1551.
- Meyer, F.P. and Jorgenson, T.A., 1983.** Teratological and other effects of malachite green on development of rainbow trout and rabbits. *Transactions of the American Fisheries Society*, 112, 818–824.
- Meyer, F.P., 1991.** Aquaculture disease and health management. *Journal of Animal Science*, 69, 4201–4208.
- Morones, J.R., Elechiguerra, J.L., Camacho, A. and Ramirez, J.T., 2005.** The bactericidal effect of silver nanoparticles. *Nanotechnology*, 16, 2346–2353.
- Muzzarelli, R.A.A., Muzzarelli, C., Tarsi, R., Miliani, M. and Cartolari, M., 2001.** Fungistatic activity of modified chitosans against *Saprolegnia parasitica*. *Biomacromolecules*, 2, 165–169.
- Noga E. J., 1993.** Water mold infections of freshwater fish: Recent advances. *Annual Review of Fish Diseases*, 3, 291–304.
- Olah, J. and Farkas, J., 1978.** Effect of temperature, pH, antibiotics, formalin, and malachite green on the growth and survival of *Saprolegnia* and *Achyla* parasites on fish. *Aquaculture*, 13, 273–288.
- Oya, A., 1996.** A series of lectures on practical inorganic antibacterial agents-opening lecture. *Journal of Antibacterial and Antifungal Agents*, 24, 429–432.
- Petersen, A., Jegstrup, I. and Olson, L.W., 1994.** Screening for bacteria antagonistic to *Saprolegnia parasitica* with BASF pluronic polyol- F-127. In: Mueller, G.J. (ed.) *Salmon Saprolegniasis*. US Department of Energy, Portland, DOE/BP-02836-1. pp. 149–160.
- Pickering, A.D. and Willoughby, L.G., 1982.** *Saprolegnia* infections of salmonid fish. pp. 38–48 in 50th Annual Report. Institute of Freshwater Ecology. 16, 1–9.
- Pottinger, T.G. and Day, J.G., 1999.** *Saprolegnia parasitica* challenge

- system for rainbow trout: Assessment of Pyceze as an anti-fungal agent for both fish and ova. *Diseases of Aquatic Organisms*, 36, 129–141.
- Prabhu, S. and Poulouse, E.K., 2012.** Silver nanoparticles: Mechanism of antimicrobial action, synthesis, medical applications, and toxicity effects. *International Nano Letters*, 3, 21–28.
- Rai, M., Yadav, A. and Gade, A., 2009.** Silver nanoparticles as a new generation of antimicrobials. *Biotechnology Advances*, 27, 76–83.
- Rahkonen, R. and Koski, P., 2002.** Post malachite green: Alternative strategies for fungal infections and white spot disease. *Bulletin of the European Association of Fish Pathologists*, 22, 152–157.
- Richmond, D.V., 1977.** Permeation and migration of fungicides in fungal cells. In: Siegel, M.R. and Sisler, H.D. (eds) *Antifungal Compounds*, Volume 2. Interactions in Biological and Ecological Systems. Marcel Dekker, Inc., New York. pp. 251–276.
- Sadjadi, M. S., Farhadyar, N. and Zare, K., 2009.** Biocatalytic activity of fungal protease on silver nanoparticle-loaded zeolite X microspheres. *Journal of Nanoscience and Nanotechnology*, 9, 1365–1368.
- Sanpui, P., Murugadoss, A., Prasad, P.V.D., Ghosh, S.S. and Chattopadhyay, A., 2008.** The antibacterial properties of a novel chitosan–Ag-nanoparticle composite. *International Journal of Food Microbiology*, 124, 142–146.
- Schreier, T.M., Rach, J.J. and Howe, G.E., 1996.** Efficacy of formalin, hydrogen peroxide, and sodium chloride on fungal-infected rainbow trout eggs. *Aquaculture*, 140, 323–331.
- Shahbazian, N., Mousavi, Ebrahimzadeh, M.H.A, Soltani, M. and Khosravi, H.A., 2010.** Fungal contamination in rainbow trout eggs in Kermanshah province propagation with emphasis on Saprolegniaceae. *Iranian journal of fisheries sciences*, 9, 151–160.
- Shameli, K., Ahmad, M.B. and Yunus, W.M.Z.W., 2010.** Synthesis and characterization of silver/talc nanocomposites using the wet chemical reduction method. *International Journal of Nanomedicine*, 5, 743–751.
- Somers, E., 1967.** The detoxification of fungicides by fungal spores. In: Symposium Reinhardtsbrunn. Akademie-Verlag, Berlin. pp. 325–331.
- Song, H.Y., Ko, K.K., Oh, L.H. and Lee, B.T., 2006.** Fabrication of silver nanoparticles and their antimicrobial mechanisms. *European Cells and Materials*, 11, 58–63.
- Srivastava, S., Sinha, R. and Roy, D., 2004.** Toxicological effects of malachite green. *Aquatic Toxicology*, 66, 319–329.
- Top, A. and Ulku, S., 2004.** Silver, zinc, and copper exchange in a Naclinoptilolite and resulting effect

- on antibacterial activity. *Applied Clay Sciences*, 27, 13-19.
- Van West, P., 2006.** *Saprolegnia parasitica*, an oomycete pathogen with a fishy appetite: New challenges for an old problem. *Mycologist*, 20, 99-104.
- Willoughby, L.G. and Pickering, A.D., 1977.** Viable Saprolegniaceae spores on the epidermis of the salmonid fish *Salmo trutta* and *Salvelinus alpinus*. *Mycology Society*, 68, 91-95.
- Willoughby, L.G. and Roberts, R.J., 1992.** Towards strategic use of fungicides against *Saprolegnia parasitica* in salmonid fish hatcheries. *Journal of Fish Diseases*, 15, 1-13.
- Walser, C.A. and Phelps, R.P., 1993.** The use of formalin and iodine to control *Saprolegnia* infections on channel catfish, *Ictalurus punctatus*, eggs. *Journal of Applied Aquaculture*, 3, 269-278.
- Xu, G., Qiao, X., Qiu, X. and Chen, J., 2011.** Preparation and characterization of nano-silver loaded montmorillonite with strong antibacterial activity and slow release property. *Journal of Material Science and Technology*, 27, 685-690.
- Yamamoto, K., Ohashi, S., Aono, M., Kokubo, T., Yamada, I. and Yamauchi, J., 1996.** Antibacterial activity of silver ions implanted in SiO₂ filler on oral streptococci. *Dental Materials*, 12, 227-229.
- Yamanaka, M., Hara, K. and Kudo, J., 2005.** Bactericidal action of a silver ion solution on *Escherichia coli*, studied by energy-filtering transmission electron microscopy and proteomic analysis. *Applied and Environmental Microbiology*, 11, 7589-7593.
- Yoshihiro, I., 2002.** Bactericidal activity of Ag zeolite mediated by reactive species under aerated conditions. *Journal of Inorganic Biochemistry*, 92, 37-42.
- Zhou, Y., Xiab, M., Ye, Y. and Hu, C., 2004.** Antimicrobial ability of Cu²⁺-montmorillonite. *Applied Clay Science*, 27, 215-218.